

# The Effect of Surface Roughness of Substrates on the Performance of Polycrystalline Cadmium Sulfide/Cadmium Telluride Solar Cells

K. Balashangar<sup>1</sup>, M. Thanihaichelvan<sup>1</sup>, P. Ravirajan<sup>1,\*</sup>, G. D. K. Mahanama<sup>2</sup>,  
M. A. K. L. Dissanayake<sup>3</sup>, E. Colegrove<sup>4,5</sup>, R. G. Dhere<sup>5</sup>, and S. Sivananthan<sup>4,5</sup>

<sup>1</sup>Department of Physics, University of Jaffna, Thirunelveli, JA 40000, Sri Lanka

<sup>2</sup>Department of Physics, University of Ruhuna, Matara, Sri Lanka

<sup>3</sup>Institute of Fundamental Studies, Kandy, Sri Lanka

<sup>4</sup>Department of Physics, University of Illinois at Chicago, USA

<sup>5</sup>Sivananthan Laboratories Inc., Bolingbrook, USA

The cadmium sulfide (CdS)/cadmium telluride (CdTe) heterojunction is a promising material combination for the development of cost efficient solar cells to meet the world's future energy demand. This study examined the effects of the surface roughness of six different layers, such as FTO, SnO<sub>2</sub> buffered FTO, thick and thin CdS layers deposited on these buffered and unbuffered FTO, on the photovoltaic performance of the corresponding CdS/CdTe solar cells. The morphologies of these surfaces were examined by atomic force microscopy (AFM). The short circuit current densities and fill factors of the devices were improved significantly when the SnO<sub>2</sub> buffer layer was introduced between the FTO and CdS layer. AFM images showed that surface roughness of the FTO coated glass substrates decreased when a buffer layer was present on FTO. The short circuit current densities and hence the external quantum efficiencies were improved further when the thickness of the CdS layer was reduced. This was attributed to the reduced filtering effect of the CdS layer. The optimized device showed an external quantum efficiency of more than 85% at the maximum absorption wavelengths of CdTe and an overall power conversion efficiency of more than 14.5% under an air mass (AM) 1.5 irradiation (100 mW cm<sup>-2</sup>, 1 sun).

**Keywords:** CdTe Solar Cells, Surface Roughness, Buffer Layer, External Quantum Efficiency.

## 1. INTRODUCTION

Cadmium telluride (CdTe) has attracted considerable interest among several candidates for thin-film solar cell with significant ability to convert light into electricity.<sup>1–3</sup> CdTe solar cells have a favorable fabrication cost, processing methods and stability.<sup>4</sup> Solar cells produced using CdTe have reached adequate technological maturity to be one of the most successful photovoltaic technologies in the market.<sup>5,6</sup> The latest world record efficiency for cadmium-telluride (CdTe) photovoltaic (PV) module was 17.0% in May 2014 and the research cell efficiency of 21% was achieved by First Solar, Inc. in August 2014.<sup>7,8</sup> The fabrication of flexible and light weight CdS/CdTe solar cells has also attracted considerable interest for very high specific power and flexibility for curved shaping or rolling in terrestrial and space applications.<sup>9–12</sup>

CdTe is a group II<sup>B</sup>–VI<sup>A</sup> compound semiconductor with a direct optical band gap that is almost optimally matched to the solar spectrum for photovoltaic energy conversion. The high quantum yield can be expected over a wide wavelength range because of the direct band gap ( $E_g = 1.5$  eV) and high absorption coefficient ( $>5 \times 10^5/\text{cm}$ ) of CdTe.<sup>13–15</sup>

In conventional CdTe cells, polycrystalline cadmium sulfide (CdS) is used as the best suited *n*-type heterojunction partner over the last few decades.<sup>16</sup> CdS has been used as a window layer in solar cells owing to its wide band gap (2.42 eV).<sup>17</sup> The majority of studies of CdS/CdTe solar cells have been conducted in the superstrate configuration because all CdTe modules currently in commercial production were constructed in this configuration.<sup>18</sup> In the superstrate configuration, light enters the junction through a transparent substrate, typically soda lime glass. One of advantages of the superstrate design is that the

\*Author to whom correspondence should be addressed.

surface of the CdTe is accessed easily for the formation of a back contact. The substrate-structured devices have also attracted interest as possible solar cells in flexible materials, such as high temperature polymers and ceramics.<sup>19</sup> Figures 1(a) and (b) present a schematic diagram of the superstrate and substrate device structures, respectively. The superstrate structure has a fluorine doped tin oxide (FTO) layer as the front contact and copper (Cu) followed by a gold (Au) layer as the top contact.

In superstrate structured devices, the formation of CdTe occurs after the growth of CdS thin films during the fabrication process. At high temperatures, the formation of  $\text{CdTe}_{1-x}\text{S}_x$  is observed at the CdS–CdTe interface, and it was reported that the formation of  $\text{CdTe}_{1-x}\text{S}_x$  ternary decreases the cell efficiency.<sup>20,21</sup> The formation of a  $\text{CdTe}_{1-x}\text{S}_x$  ternary compound is due to the inter diffusion of CdTe into the CdS layer.<sup>22</sup> The interdiffusion depends on the nature and surface roughness of the CdS window layer and the residual oxygen present in the CdS surface prior to CdTe deposition. The CdS–CdTe interface was also reported to have a significant impact on the device performance.<sup>23</sup>

This study examined the correlation between the surface smoothness of the CdS window layer and the conversion efficiencies of the cells. The surface of the CdS film grown by chemical bath deposition (CBD) over bare fluorine-doped tin oxide (FTO) and undoped tin oxide ( $\text{SnO}_2$ ) coated FTO glasses were characterized by atomic force microscopy (AFM).

## 2. EXPERIMENTAL PROCEDURES


Pilkington TEC 15 FTO glass was used for solar cell fabrication and  $\text{SnO}_2$  buffer layers were deposited by chemical vapor deposition at the National Renewable Energy Laboratory (NREL), USA, as outlined in Ref. [24].<sup>24</sup> CdS thin films were grown by chemical bath deposition (CBD) on cleaned FTO and  $\text{SnO}_2$  coated FTO substrates, where

as polycrystalline CdTe films were deposited by close spaced sublimation (CSS) on the CdS layer, as described in Ref. [25].<sup>25</sup> The active layers were annealed in  $\text{CdCl}_2$  vapor by CSS to improve the crystallinity and grain size of CdTe.<sup>26</sup> All samples were etched in a nitric acid-phosphoric acid (NP) solution to remove the surface oxides and create a tellurium-rich CdTe surface after the  $\text{CdCl}_2$  treatment. Copper and gold layers were deposited using an electron beam physical vapor deposition under a good vacuum ( $10^{-6}$  torr). To improve the ohmic contact, the samples were then annealed in flowing nitrogen to promote Cu diffusion and facilitate the formation of  $\text{Cu}_x\text{Te}$ .<sup>27</sup>

In each substrate ( $1.5'' \times 1.5''$ ), sixteen devices were fabricated. Two thicknesses of CdS (referred as thick and thin CdS layers) on the  $\text{SnO}_2$  buffered and bare FTO glass substrates were used, keeping the thickness of the active CdTe layer constant. The surface roughness of the bare and buffered FTO glasses, and the samples with the thick and thin CdS layers deposited on buffered and unbuffered FTO glass were measured by AFM. The absorption spectra were measured by ultraviolet-visible-near infrared (UV-VIS-NIR) spectroscopy. The photovoltaic performance of the fabricated solar cells was measured under illumination of 1 sun (air mass 1.5), and the external quantum efficiency (EQE) measurements were taken using a computer interfaced source measure unit (Keithley 2400) and a monochromator.

## 3. RESULTS AND DISCUSSION

Figure 2 shows the photovoltaic performance of the four different types of solar cells fabricated and characterized in this study. Figures 2(a) and (b) clearly show that the presence of a buffer layer improves the power conversion efficiency and short circuit current density ( $J_{sc}$ ), particularly in a device with a thin window layer, but there were no significant changes in the open circuit voltage ( $V_{oc}$ ) (Fig. 2(c)) of the thick window layer cells. In contrast,

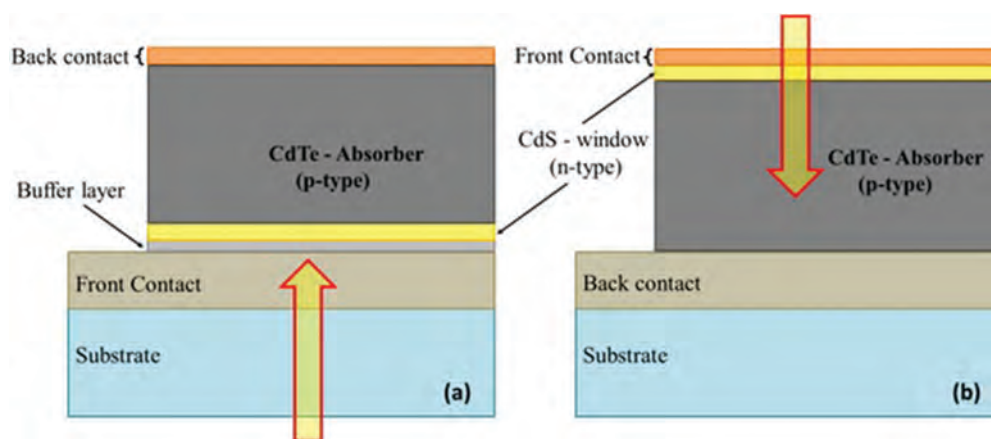

**Fig. 1.** Schematic diagram of cross-section of a CdTe solar cell in (a) superstrate, and (b) substrate configuration, where the arrows show the direction of illumination.

4. M. Woodhouse, A. Goodrich, R. Margolis, T. James, R. Dhere, T. Gessert, T. Barnes, R. Eggert, and D. Albin, *Sol. Energy Mater. Sol. Cells* 115, 199 (2013).
5. A. Romeo, CdTe thin film solar cells: Present status and future perspectives, *AIP Conference Proceedings* (2011), Vol. 1391, p. 33.
6. P. V. Meyers, *Solar Cells* 23, 59 (1988).
7. First Solar I. First Solar Sets Thin-Film Module Efficiency World Record of 17.0 Percent. <http://investor.firstsolar.com/releasedetail.cfm?ReleaseID=8339712014> [Accessed 23.05.2014] (2014).
8. Inc. First Solar, First Solar Builds the Highest Efficiency Thin Film PV Cell on Record, <http://investor.firstsolar.com/releasedetail.cfm?ReleaseID=864426> [Accessed 08 August 2014] (2014).
9. A. N. Tiwari, A. Romeo, D. Baetzner, and H. Zogg, *Progress in Photovoltaics: Research and Applications* 9, 211 (2001).
10. J. P. Enriquez, X. Mathew, G. Hernández, U. Pal, C. Magaña, D. Acosta, R. Guardian, J. A. Toledo, P. G. Contreras, and J. A. Chávez, *Sol. Energy Mater. Sol. Cells* 82, 307 (2004).
11. X. Mathew, J. P. Enriquez, A. Romeo, and A. N. Tiwari, *Solar Energy* 77, 831 (2004).
12. L. Kranz, C. Gretener, J. Perrenoud, R. Schmitt, F. Pianezzi, F. La Mattina, P. Blösch, E. Cheah, A. Chirilă, C. M. Fella, H. Hagendorfer, T. Jäger, S. Nishiwaki, A. R. Uhl, S. Buecheler, and A. N. Tiwari, *Nature Communications* 4 (2013).
13. B. E. McCandless and J. R. Sites, Cadmium telluride solar cells, *Handbook of Photovoltaic Science and Engineering*, John Wiley & Sons, Ltd. (2005), pp. 617–662.
14. A. Morales-Acevedo, *Solar Energy* 80, 675 (2006).
15. J. Sites, and J. Pan, *Thin Solid Films* 515, 6099 (2007).
16. J. Britt and C. Ferekides, *Appl. Phys. Lett.* 62, 2851 (1993).
17. I. M. Dharmadasa, *Advances in Thin-Film Solar Cells*, CRC Press, Pan Stanford (2012).
18. J. Poortmans and V. Arkhipov, *Thin Film Solar Cells: Fabrication, Characterization and Applications*, John Wiley & Sons, Ltd (2006).
19. R. G. Dhere, J. N. Duenow, C. M. DeHart, J. V. Li, D. Kuciauskas, and T. A. Gessert, Development of substrate structure CdTe photovoltaic devices with performance exceeding 10%, *2012 38th IEEE Photovoltaic Specialists Conference (PVSC)*, Austin, Texas, June (2012).
20. O. Keiichi, S. Junji, and T. Tetsuro, *Jpn. J. Appl. Phys.* 12, 1641 (1973).
21. A. D. Compaan, J. R. Sites, R. W. Birkmire, C. S. Ferekides, and A. L. Fahrenbruch, Critical issues and research needs for cdte-based solar cells, *Photovoltaics for the 21st Century Electrochemical Society Symposium* (1999).
22. I. Dharmadasa, *Coatings* 4, 282 (2014).
23. D. H. Rose, D. H. Levi, R. J. Matson, D. S. Albin, R. G. Dhere, and P. Sheldon, Role of oxygen in CdS/CdTe solar cells deposited by close-spaced sublimation, *Conference Record of the Twenty Fifth IEEE Photovoltaic Specialists Conference*, Washington, DC, May (1996).
24. X. Li, R. Ribelin, Y. Mahathongdy, D. Albin, R. Dhere, D. Rose, S. Asher, H. Moutinho, and P. Sheldon, Effect of high-resistance SnO<sub>2</sub> on CdS/CdTe device performance, *NCPV Photovoltaics Program Review: Proceedings of the 15th Conference*, American Institute of Physics, Denver, Colorado, September (1998).
25. D. H. Rose, F. S. Hasoon, R. G. Dhere, D. S. Albin, R. M. Ribelin, X. S. Li, Y. Mahathongdy, T. A. Gessert, and P. Sheldon, *Progress in Photovoltaics: Research and Applications* 7, 331 (1999).
26. S. A. Ringel, A. W. Smith, M. H. MacDougall, and A. Rohatgi, *J. Appl. Phys.* 70, 881 (1991).
27. C. R. Corwine, A. O. Pudov, M. Gloeckler, S. H. Demtsu, and J. R. Sites, *Sol. Energy Mater. Sol. Cells* 82, 481 (2004).
28. J. Y. Choi, K.-J. Kim, J.-B. Yoo, and D. Kim, *Solar Energy* 64, 41 (1998).

Received: xx Xxxx xxxx. Accepted: xx Xxxx xxxx.