


Accepted Manuscript

Interaction of arsenic with biochar in soil and water: A critical review

Meththika Vithanage, Indika Herath, Stephen Joseph, Jochen Bundschuh, Nanthi Bolan, Yong Sik Ok, M.B. Kirkham, Jörg Rinklebe

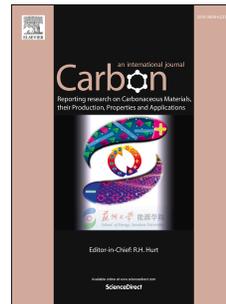

PII: S0008-6223(16)31006-5

DOI: [10.1016/j.carbon.2016.11.032](https://doi.org/10.1016/j.carbon.2016.11.032)

Reference: CARBON 11476

To appear in: *Carbon*

Received Date: 30 July 2016

Revised Date: 26 October 2016

Accepted Date: 15 November 2016

Please cite this article as: M. Vithanage, I. Herath, S. Joseph, J. Bundschuh, N. Bolan, Y.S. Ok, M.B. Kirkham, J. Rinklebe, Interaction of arsenic with biochar in soil and water: A critical review, *Carbon* (2016), doi: 10.1016/j.carbon.2016.11.032.

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

Interaction of Arsenic with Biochar in Soil and Water: A Critical Review

Meththika Vithanage^{a,b*}, Indika Herath^c, Stephen Joseph^d, Jochen Bundschuh^e, Nanthi Bolan^f, Yong Sik Ok^g, M. B. Kirkham^h, Jörg Rinklebe^{i*}

^a*Chemical and Environmental Systems Modeling Research Group, National Institute of Fundamental Studies, Hantana Road, Kandy 20000, Sri Lanka. E-Mail: meththikavithanage@gmail.com*

^b*School of Civil Engineering and Surveying and the International Centre for Applied Climate Science, University of Southern Queensland (USQ), West Street, Toowoomba, Queensland 4350, Australia*

^c*Faculty of Health, Engineering and Sciences, University of Southern Queensland (USQ), West Street, Toowoomba, Queensland 4350, Australia. E-Mail: Indika.Herath@usq.edu.au*

^d*School of Materials Science and Engineering, University of NSW, Sydney NSW 2052, Australia. Email: joey.stephen@gmail.com*

^e*University of Southern Queensland, West Street, Toowoomba, Queensland 4350, Australia. E-Mail: Jochen.Bundschuh@usq.edu.au*

^f*Global Centre for Environmental Remediation (GCER), Faculty of Science and Information Technology, The University of Newcastle, University Drive, Callaghan NSW 2308, Australia. Email: Nanthi.Bolan@newcastle.edu.au*

^g*Korea Biochar Research Center & School of Natural Resources and Environmental Science, Kangwon National University, Chuncheon 200-701, Korea. Email: soilok@kangwon.ac.lk*

^h*Department of Agronomy 2004 Throckmorton Plant Sciences Center, Kansas State University, Manhattan, KS 66506 United States. Email: mbk@k-state.edu*

ⁱ*University of Wuppertal, Soil- and Groundwater-Management, Pauluskirchstraße 7, 42285 Wuppertal, Germany. Email: rinklebe@uni-wuppertal.de*

*Co-corresponding authors:

Meththika Vithanage, Tel: +94 8122 32 002. Fax: +94 8122 32 131

E-Mail: meththikavithanage@gmail.com

Jörg Rinklebe, Tel: +49 202 439 4057. Fax: +49 202 439 4196

E-mail: rinklebe@uni-wuppertal.de

33 Abstract

34 Biochar exhibits a great potential to act as a universally applicable material for water and soil
35 remediation due to extensive availability of feedstocks and favorable physio-chemical surface
36 characteristics; nevertheless, studies related to its application on the remediation of toxic metalloids
37 are relatively rare. Hence, this review highlights biochar production technologies, biochar
38 properties, and recent advances in the removal and immobilization of a major metalloid
39 contaminant, As in water and soil. It also covers surface modification of biochars to enhance
40 contaminant removal and microbial properties in biochar amended soil. Experimental studies
41 related to the adsorption behaviors of biochar and the underlying mechanisms proposed to explain
42 them have been comprehensively reviewed. Compared to the number of research publications in
43 SCOPUS database on “Biochar+Water” (≈ 1290 – Scopus), the attention drawn to examine the
44 behavior of biochar on the remediation of As is limited (≈ 85 - Scopus). Because of the toxicity of
45 As, the subject urgently needs more consideration. In addition to covering the topics listed above,
46 this review identifies research gaps in the use of biochar as an adsorbent, and proposes potential
47 areas for future application of biochars.

48
49 **Keywords:** Bioavailability, Phytotoxicity, Charcoal, Black carbon, Activated carbon, Slow
50 pyrolysis

51

52

53 **Content**

54 1. Introduction

55 1.1. Research on arsenic and biochar

56 2. Production and properties of biochar

57 3. Application of biochar for As remediation in water

58 3.1. Arsenic remediation by non-activated biochar

59 3.1.1. Effect of pH

60 3.1.2. Effect of redox conditions

61 3.1.3. Kinetics and isotherm aspects for As-biochar interactions

62 3.2. Use of modified biochar for As treatment

63 4. Application of biochar in As contaminated soil

64 4.1. Response of soil physio-chemical properties of As-contaminated soils to biochar

65 4.2. Role of biochar on As in soil

66 4.3. Response of microbiological properties in biochar-amended As contaminated soils

67 5. Summary and future research

68 References

69

70

71

72

73

74

75

76 1. Introduction

77 Arsenic (As) is the 20th most abundant element in the geosphere, and the 14th in seawater. However
78 it has been recognized as an extremely toxic metalloid for humans as well as for fauna and flora [1-
79 3]. The mean amount of As in the earth's crust is known to be approximately 1.8 mg/kg [4], but this
80 number is increased due to anthropogenic pollution. Inorganic anionic As species, arsenite [As(III)]
81 and arsenate [As(V)], as well as organic species, particularly mono-, di- and, tri- methyl arsenates,
82 have been recognized as major toxic species of As in natural water systems. Furthermore, more
83 noxious organic and inorganic thio-As species can be found widely in geothermal and marine
84 environments [5-6]. Elevated concentrations of As in groundwater have been reported in many parts
85 of the world [7]. Interestingly every year, some new locations are found with high background
86 arsenic concentrations. As noted, As can be found in soils due to both geogenic and anthropogenic
87 activities, and it may occur at a wide range of concentrations, ranging from $\mu\text{g}/\text{kg}$ levels to
88 extremely high concentrations such as 250,000 mg/kg [8-9]. The levels of As is extremely minute to
89 be a causative factor for health issues and hence, the safe permissible value has kept very low
90 compared to other toxic metals (10 $\mu\text{g}/\text{L}$) by the World Health Organization (WHO).

91 A variety of technologies such as chemical oxidation, precipitation, adsorption, ion exchange,
92 reverse osmosis, and membrane separation has been adopted for the removal of As in water and
93 wastewater. Adsorption is considered as an effective remediation strategy due to its low cost and
94 relatively simple design [10-12]. However, the removal of As from aqueous solutions is a serious
95 challenge for researchers, engineers, and technologists due to varying As speciation depending on
96 pH of the media. Few studies have confirmed the application of some materials that are efficient in
97 remediating both As(III) and As(V) species irrespective of the pH [13-14]. Interactions of
98 microorganisms with different As species also are important in remediating As contaminated

99 environmental systems [15]. Up to date, many materials, such as titanium carbonitride-derived
100 adsorbents, agricultural wastes (rice husks), and iron oxide granules, which have been tested for As
101 remediation, are either speciation specific or pollutant-specific, and, hence, they are not applicable
102 for the simultaneous removal from a mixture of contaminants in aqueous solutions. Therefore,
103 explore materials that can be used for the simultaneous remediation of many different pollutants and
104 their species may receive strong attention. Activated carbon covers a wide spectrum of applications
105 in drinking water treatment due to its high performance, high surface area, mechanically strong
106 properties and avoids chemical waste products that need to be added in other applications.
107 However; it is hardly applicable for soil remediation due to the cost involved in the production [16].
108 Hence, currently focus has been drawn to biochar, because it is a cost effective and environmentally
109 feasible carbonaceous product derived by the pyrolysis of certain feedstocks that has applications in
110 a variety of contaminated environments [17-18]. However, yet biochar has not achieved high
111 surface area as in the case of Activated carbon and poor in mechanical properties hence, it limits the
112 application into water treatment.

113 In the past decade, biochar has been experimented extensively in various agricultural and
114 environmental problems, due to its strong influence on immobilization of contaminants,
115 improvement in soil health, and carbon sequestration in relation to climate change [19-20]. In
116 addition, research has revealed that biochar also has an affinity for, and can retain, both heavy
117 metals and organic compounds that contaminate wastewaters [17, 21]. Moreover, biochar can be
118 produced from residues that are often burnt in fields or buried in landfill, thus having a triple line
119 benefit namely economic, reduction in polluted soil and water and production of renewable energy
120 [22]. Many studies have reported an excellent ability of biochars to remove heavy metals, organic

121 pollutants, and other pollutants from aqueous solutions [17-18, 21-23]. Due to the above-revealed
122 factors, research on biochar have been increasing at an exponential rate over the past few years.

123

124 *1.1. Research on arsenic and biochar*

125 The use of charcoal in agriculture or, biochar, as it is now referred to is a millennium old practice
126 in all continents but specifically in Japan and China, Brazil, India, Australia and parts of Africa[24-
127 25][30]. Studies of it use has shown that soils where charcoal has been incorporated for centuries
128 have result in soils that are much more fertile than the surrounding soils Publications related to As
129 adsorptive remediation both in soil and water environment during the years from 1980 to 2014
130 (according to ISI Web of Science™) have been growing steadily [Fig. 1]. The figure shows the
131 growing interest of the scientific community on As remediation research, and the trend on the As
132 remediation in soil and water has extended from the phase of scientific research to engineering
133 applications. There has been a significant increase during the last decade of field scale and pot
134 experiments that have been conducted to investigate the effectiveness of biochar as a soil
135 amendment to immobilize As [26-27]. However, there is still a gap between research focused on
136 soil remediation and research on As remediation in aqueous media [Fig. 1(a)]. Only a few studies
137 are focused on As immobilization in soil than the water research. At the same time, there has not
138 been a centre of attention to understand the As mobilization/release mechanisms due to the
139 application of different biochar produced from various production technologies.

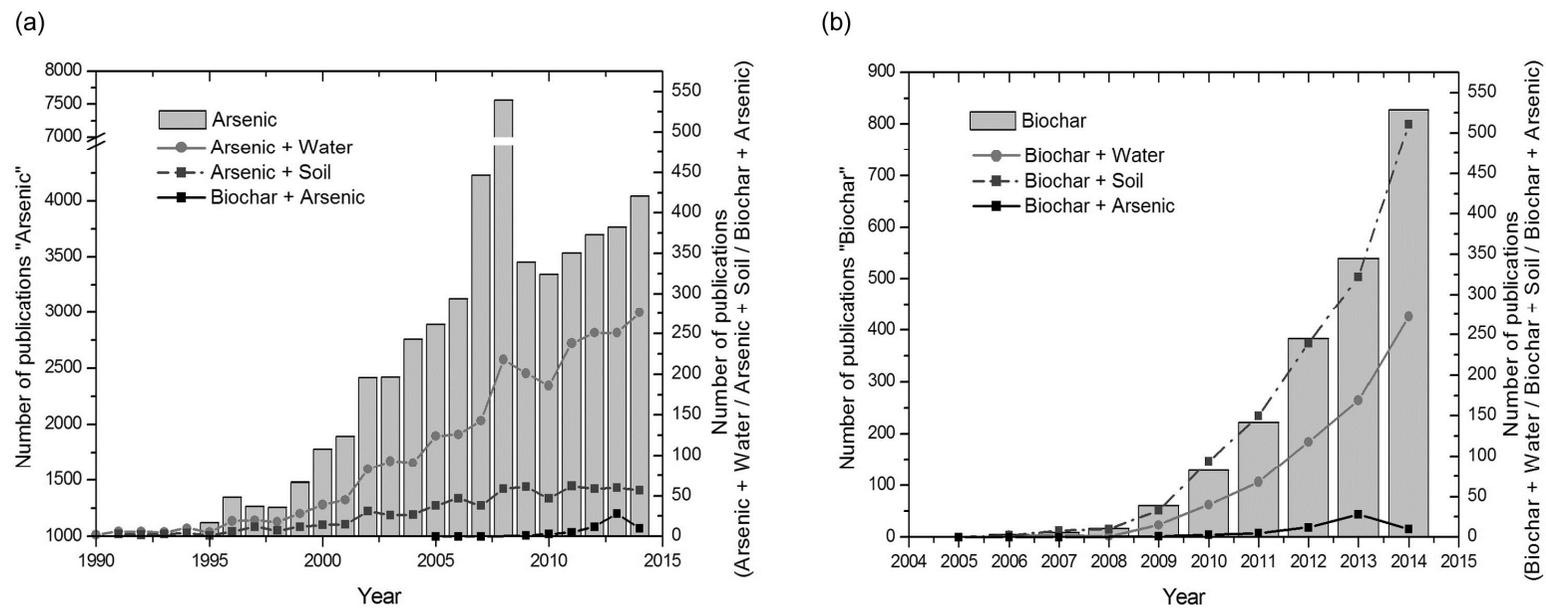


Fig. 1. Science Citation Indexed publications on As (a) and biochar (b) in SCOPUS

Existing publications on biochar mainly deal with its application in technical, economical, climate-related aspects; soil quality and remediation; and remediation of water and wastewater [17, 20-21, 28-31]. With the increasing interest in scientific research on biochar and its surface modifications, an integrated understanding of the mechanisms of biochar to remediate As in contaminated water and soils via enhancing functional aspects of biochar for future engineering scale applications. Hence, the aim of this review is to analyze recent literature related to the application of biochar for the immobilization and/or removal of As in soil and water environments. This review further summarizes the recent developments in the preparation and properties of pristine (non-activated) and engineered biochar, as well as the mechanisms involved in the adsorption of As with regard to water and soil aspects.

2. Production and properties of biochar

Biochar production technologies and their properties have been well reviewed [17, 21]. Tan et al. [21] have demonstrated that slow pyrolysis is the most commonly used technology for the production of biochar that can be used widely in water and wastewater treatment. Biochar can be produced from invasive plants, crop residues, woody biomass, animal litter, bones, and municipal solid wastes by using various thermochemical processes (e.g., slow pyrolysis, fast pyrolysis, hydrothermal carbonization, flash carbonization, torrefaction, and gasification) (Fig. 2) [32-33].

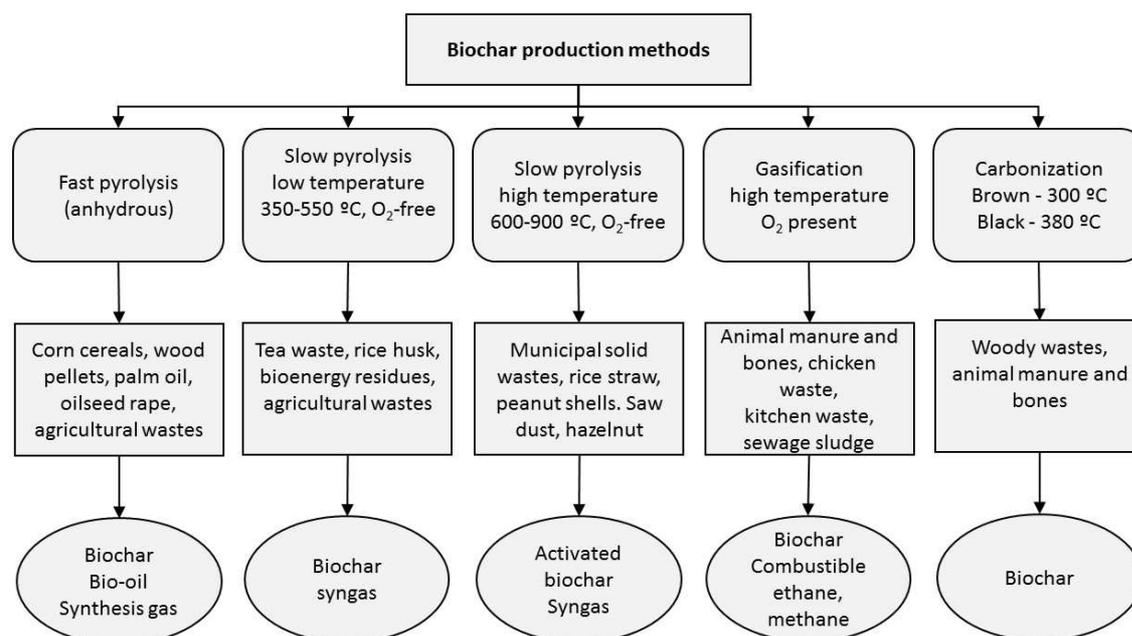


Fig. 2. Schematic representation of biochar production methods with regard to their common feedstock types (adapted from [34]).

The yield of biochar and its characteristic features depend on the thermochemical processes, operating conditions, and feedstock. It has been well established that the low temperature derived biochars from slow pyrolysis result in low hydrophobicity and aromaticity but in high surface acidity and polarity. Major biomass decomposition tends to occur between 200 and 500 °C via several steps including, partial hemicellulose decomposition, complete hemicellulose decomposition, and full cellulose and partial lignin decomposition [35]. The content of ash in biochar can have an impact on the immobilization of contaminants, and it tends to increase gradually with rising pyrolysis temperatures. The ash content of pine needle biochar produced at 700 °C was nearly 10-fold higher than that of its biomass, which was likely due to the

accumulation of alkaline minerals and organic matter with the increase of the pyrolytic temperature [36]. The elemental composition of biochar changes with the pyrolytic temperature and depends on the type of feedstock. Carbon content tends to increase with increasing production temperature, while nitrogen, sulfur, hydrogen, and oxygen, which form gaseous products during pyrolysis, decrease [17, 37]. Biochars produced from biosolids and animal manures typically contain high amounts of N, P, K and S [17, 23, 37-38]. Biochars derived from plant biomass, manure, and biosolids generally are characterized by having high N, P, K, and S compared to biochars produced from woody feedstocks. Liard et al. [38] showed that nearly half of the N and S can be lost during pyrolysis when temperature increases from 350 to 600 °C. The same authors found that the residual N in biochar is not bioavailable, whereas the bioavailability of phosphorus depends on soil pH. Hence P shows a low bioavailability in calcareous soils and a high bioavailability in acidic soils.

Physical characteristics, including pore structure, surface area, and adsorption properties, are related to the pyrolytic temperature and feedstock composition [39-40]. Volatile compounds that are present in the feedstock tend to be removed from the matrix with increasing pyrolytic temperature. This enhances the surface area and ash content while decreasing the surface functional groups along with exchange sites. With increasing pyrolytic temperature, aliphatic carbon species are converted into aromatic rings forming a graphene like structure that improves the pore distribution, pore volume, and surface area of the biochar [17]. Biochars containing large amounts of C in condensed aromatic rings tend to possess few functional groups. Surface functional groups play a crucial role in the adsorption capacity of biochar, and the content and type of functional groups are dependent on the feedstock and the pyrolytic temperature [41-42]. Low-temperature chars with low aromaticity contain more C=O and C-H functional groups that

promote adsorption for contaminants [43]. The molar oxygen to carbon (O/C) ratio is an indication of the surface hydrophilicity and can be used to estimate the polar functional groups present on the biochar surface [44]. At higher temperatures, the O/C ratio is low indicating more aromatic and fewer hydrophilic surfaces due to high carbonization and loss of polar functional groups [44]. The (O + N)/C ratio serves as an indicator of polarity. It decreases with increasing pyrolytic temperature [44].

In addition to slow pyrolysis, hydrothermal carbonization is another, efficient thermochemical technology to produce biochar. It results in high carbon yield. Compared to slow pyrolysis, hydrothermal carbonization is high in energy consumption. Although hydrothermal carbonization uses unconventional wet biomass sources the thermal energy depends on the moisture content and the water to solid ratio that is needed [45]. Biochars produced by hydrothermal carbonization are high in oxygen functional groups and cation exchange capacity (CEC). They are more acidic than biochars produced under slow pyrolysis [46-47]. However, hydrothermal carbonization biochars are readily biodegradable and, hence, the slow pyrolysis biochar is more stable and has a higher potential for carbon sequestration [17]. Nevertheless, pot trials have shown low yields in hydrochars compared to chars from slow pyrolysis [48].

Little information has been reported regarding the application of biochars produced from flash carbonization, torrefaction, and gasification technologies in the remediation of pollutants in wastewaters, because these technologies focus on the production of bio-oil, solid fuel, or synthetic gas. Flash carbonization is used to produce biochar through the detonation of a flash fire at high pressure (at about 1-2 MPa) in a packed bed of biomass. Fast pyrolysis rapidly can heat biomass to produce predominately bio-oil, and, subsequently, gas and biochar [21]. Gasification is applied widely in the production of gases such as CO, CO₂, H₂, and N₂ at the

expense of oils and biochar. Torrefaction is a thermal pretreatment technology performed at low temperatures typically of 225-300 °C which produces biochar as a byproduct, when the biomass is pyrolysed over a long residence time (~60 min) [49-50]. The first torrefaction reaction step decomposes hemicellulose of the biomass into an unsaturated solid product (70-88 wt%) that is likely to be characteristic with typical biochar properties [32, 50]. Hence, it is clear that in flash carbonization, torrefaction, fast pyrolysis, and gasification, the biochar can be obtained as a by-product. However, the use of such biochars in wastewater treatment is perhaps not feasible due to their unfavorable properties depending on the type of pollutants [16, 51]

3. Application of biochar for As remediation in water

The capacities of biochar for As removal appear to be dependent upon the feedstocks and production technology. Biochars derived from various types of feedstocks, such as pine wood and bark, oak wood and bark, solid waste, rice husks, biosolids, and animal products, have been used to test their effectiveness on As removal from water (Table 1). However, testing of more feedstocks, such as those that are highly available as waste materials including byproducts of the

Table 1

Physio-chemical analysis of biochars used in As remediation literature.

Biochar	Temperature °C	As(III)/ As(V)	pH	EC dS/m	Proximate analysis %				Elemental analysis %				Reference
					Moisture	Ash	Volatile C	Fixed C	C	H	N	O	
Rice husk	300	As(V)	NA	NA	10.1	17.4	81.6	1.0*	NA	NA	NA	NA	[52]
Sewage Sludge	300	As(V)	NA	NA	84.5	25.9	73.7	0.4*	NA	NA	NA	NA	[52]
Solid Waste	300	As(V)	NA	NA	58.3	32.0	65.8	2.2*	NA	NA	NA	NA	[52]
MSW	400	As(V)	8.0	NA	NA	6.1	22.3	65.2	48.6	12.2	1.3	31.7	[37]
	500	As(V)	8.5	NA	NA	9.2	26.4	63.8	59.5	9.1	1.4	20.8	[37]
	600	As(V)	9.0	NA	NA	6.2	15.1	78.2	70.1	8.4	1.3	13.7	[37]
Empty fruit bunch	700	As(III)	9.4	NA	2.0	13.9	NA	NA	48.0	3.8	1.3	30.0	[13]
Rice husk	700	As(III)	8.5	NA	3.7	27.2	NA	NA	45.0	2.3	0.17	17.0	[13]
Oak wood char	400-450	As(III)	NA	NA	3.17	2.92	15.6	78.3	82.8	2.7	0.3	8.0	[11]
Pine wood char	400	As(III)	NA	NA	2.69	2.30	16.9	78.1	83.5	3.0	0.3	8.2	[53]
Oak bark char	400	As(III)	NA	NA	1.56	11.1	22.8	68.5	71.2	2.6	0.5	13.0	[16]
Sewage Sludge	550	As(III)	NA	NA	2.3	70.2	8.1	8.0	88.0	1.8	8.0	0.4	[54]
Pine cone biochar	500	As(III)	NA	NA	3.12	2.13	27.2	67.5	67.9	3.9	0.6	22.0	[55]
Pine wood biochar	600	As(V)	NA	NA	NA	4.02	NA	NA	85.7	2.1	0.3	11.2	[56]
Rice husk biochar	300-350	As(V)	10.2	2.9	NA	NA	NA	NA	7.78	NA	0.2	NA	[57]
Empty fruit bunch biochar	500	As(V)	9.5	5.3	NA	NA	NA	NA	58.1	NA	1.6	NA	[57-58]

bio-energy industries and municipal and domestic waste materials, is crucial to optimize the remediation of As contaminated waters. The remediation of both species of As, As(III) and As(V), in aqueous solution using biochar has been successful [13, 54]. Raw pine cone derived biochar and its Zn-loaded version have been used to remove As(III) from aqueous solution, with removal efficiencies of 66 and 88%, respectively [59]. Moreover, biochar produced from sewage sludge (biosolids) was highly effective (89%) in the removal of As(V) from water [10]. However, many researchers have focused only on the removal efficiency of As species in single ion systems. A limited number of studies have been conducted to understand the effect of activated and non-activated biochars on the adsorption of inorganic forms of As (III) and As(V) present in binary systems [13]. Moreover, to our knowledge, no study has been conducted to investigate the interaction of biochar with different organic species of As such as methylated and thio-arsenate compounds. This will be a challenging task in future research. Nevertheless, none of the studies paid attention on real environmental water rich in As and co-occurring ions.







3.1. As remediation by non-activated biochar

Many biochars tested for As removal are low temperature derived biochars (300 – 500 °C), as the presence of more functional groups encourages a better the adsorption of heavy metal(loid)s compared to those derived at higher temperature (Table 1).

3.1.1. Effect of pH

The pH of the medium can have an impact on charge properties of the surface of biochar as well as speciation of As. For instance, various functional groups such as amine, alcohols, carboxylic, etc. that might be present on the surface of biochar tend to be protonated depending on solution

pH, thereby changing the surface charge of biochar. On the other hand, solution pH affects the speciation of As into its different neutral and anionic forms including, H_3AsO_4 , $H_2AsO_4^-$, $HAsO_4^{2-}$, AsO_4^{3-} etc. The $H_2AsO_4^-$ species can be dominated at pH 3-6, whereas $HAsO_4^{2-}$, and AsO_4^{3-} become main species of As at $8 > \text{pH}$ [60]. Moreover, trivalent forms of As are stable at pH 0-9 as neutral H_3AsO_3 , while $H_2AsO_3^-$, AsO_3^{3-} , and AsO_3^{-3} become stable in the pH ranges 9-12, 12-13, and 13-14, respectively [61]. Therefore the adsorption mechanisms of different forms of As on certain type of adsorbents would be more complex due to different distribution capabilities of As(III) and As(V) species in aqueous solution as a function of pH. The dissociation of As species at different pHs may be expressed as following reactions [61]. Hence, different forms of As can be adsorbed on the surface of adsorbent at different pH values, so that it is quite problematic to distinguish whether the main form of As at particular pH value could be the dominated As species on the surface as well as how the As- surface complex can vary with changing solution pH. Therefore, more innovative future researches are an urgent necessity in order to understand the adsorption mechanisms of different species of As on biochar type carbon materials at different pHs.




A study conducted on pyrolysed sewage sludge used for As(III) removal showed that the adsorption capacity at two acidic pHs, which were pH 3-3.5 and pH 6-6.5, was about the same for As(III) removal [54]. However, the pH affected the equilibrium time for adsorption onto sludge biochar. There was slightly higher and faster removal at pH 6-6.5 than the lower pH [54]. In another study, the percentage As(III) removal was a 20 - 40% at pH 3 - 4 for oak wood and bark and pine bark biochars [53]. In each case, As(III) sorption decreased above pH 4.0 and the adsorption was virtually insignificant at pH 5.0 and higher [53]. Similar results have been observed for the removal of As(III) by pine cone biochar (PC) [55]. The point of zero charge (pH_{zpc}) for PC was found at pH 4.66; therefore, the biochar surface was positively charged at $pH < 4.66$; thus, the adsorption of As was higher at $pH < 4.66$. Furthermore, As(III) adsorption decreased with the increase of pH up to 7.0, which was likely due to the van der Waals interaction between the elemental As and biochar surface. Thereafter, above 7.0 pH, there was a decrease in adsorption, because of the electrostatic repulsive forces between the negatively charged surface of PC with negatively charged As(III) species [55]. The surface of biochar can itself carry both positive and negative charges at a range of pHs; however, the surface becomes net negative above its pH_{zpc} , while it is net positive below the pH_{zpc} [13, 62]. Hence, the pH_{zpc} is an important parameter, because it determines the net charge of the biochar surface for the adsorption of As.

3.1.2. Effect of redox conditions


In the soil-water-interface of many hydromorphic or wetland soils such as rice paddies, floodplains, riverine soils, marshes, bogs, and fens, redox conditions can vary [63-64]. The redox potential is one of key factors that can have an impact on the interactions between As and

biochar surface [65]. Biochar can act as an electron pump donating electrons to more oxidized species [66]. Nevertheless, the oxidation rate of biochar surface is quite a slow process and hence the biochars possess a high tendency to accept electrons from other reducing agents as well [67]. In a recent study, biochars produced from wood and grass at temperature 200-700 °C were capable of reversibly accepting and donating up to 2 mmol of electrons per gram of biochar and grass biochars having high mineral ash contents showed an increased electron exchange capacities than wood derived biochars [68].

Redox active species such, FeO(OH), MnOOH ($E^\circ - 1.5\text{V}$), MnO₂ ($E^\circ - 1.2\text{ V}$), NO₃⁻ ($E^\circ - 0.88\text{ V}$), etc. which are attached with the biochar surface can transform more mobile As(III) to less mobile As(V) species, thereby controlling the mobility of more mobile and toxic As species present in such biochar treated soil and water systems [65, 67]. It has been found that depending on the feedstock types, some biochars consist of redox active mineral phases of Fe and Mn and many of these species may exist as nanoparticles [69]. These redox active mineral phases could catalyze the redox reactions associated with different As species as tubular pores of biochar along with mineral phases have different electrochemical potentials [70]. For instance, the oxidation of As(III) to As(V) by MnO₂ is particular of concern to sequester mobile As species in soil, sediments and water systems. In this oxidation process, firstly Mn(IV) gets oxidized to Mn(III) producing an intermediate product MnOOH* (reaction 7) [7].








Secondly, the MnOOH* oxidizes H₃AsO₃ to H₃AsO₄ followed by the adsorption of reaction product of As(V) on the surface of MnO₂ (reaction 2).



Rinklebe et al. [65] observed a similar occurrence in the Eh/pH and the As immobilization mechanisms in As contaminated floodplain soil as well as in the same soil amended with biochar.

Iron can be present in biochars in the forms of iron oxide (Fe_2O_3 , Fe_3O_4 , FeOOH) depending on the pyrolysis conditions, since iron in the oxidation states of both Fe^{2+} and Fe^{+3} may be an essential element in many types of feedstocks [71]. For example, the amount of iron in a biochar derived from bio-solid feedstock has been reported to be 2.3% of the total weight of the biochar [72]. It has been found that iron oxide may be present in biochars as magnetite or hematite. The redox transformation of As(III) to less toxic As(V) and its adsorption on iron oxide has also been examined in several studies [73-75]. Moreover, the combined effects of both oxidation of As(III) and reduction of As (V) and their sorption properties on iron oxide, goethite, and magnetite have been studied under laboratory conditions [76]. The findings of this study revealed that, at pH 6-9, the As(III) is adsorbed to a similar or greater extent (reactions 9 and 10) than As(V) on iron oxide and goethite and the sorption of As(V) on both materials (reactions 11, 12, and 13) is more favorable than that of As(III) below pH 5-6 [13, 74, 76].



Understanding and application of such biochar-As-redox complexes would be a crucial alternative option in order to establish sustainable environmental management strategies for the remediation of wastewater and multi-metal polluted soil systems. However, the elucidation of the underlying mechanisms of biochar-As interactions in different soil systems still remains poorly understood and, hence, key aspects related to this topic need to be addressed by future research.

3.1.3. Kinetics and isotherm aspects for biochar-As interactions

Understanding of kinetics and isotherm aspects related to the adsorption of As on biochar surface is beneficial to examine reaction rates, effect of some variables including initial concentration of As, and re-arrangement patterns of As atoms on the surface. Adsorption of As(III) and As(V) by pristine biochars has been reported to be a function of time [10, 37, 53-55]. In studies with biochars derived from rice husk, organic fraction of municipal solid wastes and sewage sludge, the sorption of As was well described by the pseudo-second-order kinetic model.

Fitting experimental data to a pseudo-second-order model suggests the dependency of reaction rate on available binding sites in the surface of the adsorbent. The rate-limiting step may be a chemical adsorption between the biochar surface and the contaminant [37, 54-55].

Table 2 shows maximum adsorption capacities of different biochars. Highest sorption capacities were reported by Jin et al., 2014 for As(V) sorption, whereas for As(III) the maximum sorption was reported by Samsuri et al [13] for empty fruit bunch and rice husk biochars produced at 700 °C. Many studies have reported that the Langmuir model widely fits the adsorption isotherms of both As(III) and As(V) onto biochars [10, 13, 37, 53-55, 57]. Reports on thermodynamics are limited; however, only one study was found to evaluate the thermodynamic parameters necessary

to predict the feasibility of adsorption under natural conditions [55]. Interestingly, some studies have used highly unrealistic initial concentrations for their studies ranging from 50-400 mg/L [13, 57] and this could lead to bring in wrong conclusions since very high concentrations can lead into surface precipitation on solids.

ACCEPTED MANUSCRIPT

Table 2. Arsenic adsorption capacities of biochars produced from different feedstocks

Biochar	Temperature °C	As(III) /As(V)	pH	BET surface area (m ² /g)	Pore Volume (cm ³ /g)	Initial Metal Concentration (mg/L)	Optimum Adsorbent dose (g/L)	Maximum Removal	Reference
Rice husk	300	As(V)	6.7-7	155	0.153	0.90	8	2.59 µg/g	[52]
Sewage Sludge	300	As(V)	6.7-7	51	0.058	0.90	16	4.25 µg/g	[52]
Solid Waste	300	As(V)	6.7-7	5	0.029	0.90	16	3.54 µg/g	[52]
MSW	400	As(V)	6.0	21	0.027	5-400	2	24 mg/g	[37]
	500	As(V)	6.0	29	0.039	5-400	2	25 mg/g	[37]
	600	As(V)	6.0	30	0.038	5-400	2	28 mg/g	[37]
Empty fruit bunch	700	As(III)	8.0	1.89	0.011	50	5	18.9 mg/g	[13]
		As(V)	6.0	-	-	50	5	5.1 mg/g	[13]
Rice husk	700	As(III)	8.0	25.1	0.018	50	5	19.3 mg/g	[13]
		As(V)	6.0	-	-	50	5	7.1 mg/g	[13]
Oak wood char	400-450	As(III)	5.0	2.04	0.73	0.01-0.1	10	4.13 mg/g	[53]
Pine wood char	400	As(III)	5.0	2.73	0.41	0.01-0.1	10	2.62 mg/g	[53]
Oak bark char	400	As(III)	5.0	25.4	0.86	0.01-0.1	10	3.00 mg/g	[53]
Pine bark char	400	As(III)	5.0	1.88	1.06	0.01-0.1	10	13.1 mg/g	[53]
Sewage Sludge	550	As(III)	3-3.5	70	NA	1	10	0.07 mg/g	[54]
Pine cone biochar	500	As(III)	4.0	6.6	0.016	0.10	10	0.006 mg/g	[56]
Rice husk biochar	500	As(V)	9.5	23.2	0.009	0-200	2	0.35	[57]
Empty fruit bunch biochar	300-350	As(V)	10.2	46.3	0.008	0-200	2	0.42	[57]

This study revealed that the adsorption of As(III) on pine cone biochar in aqueous solution is energetically favourable (ΔG° , $-4.42 \text{ kJ mol}^{-1}$; ΔS° , $0.058 \text{ kJ mol}^{-1} \text{ K}^{-1}$) and exothermic (ΔH° , $13.25 \text{ kJ mol}^{-1}$) [55]. The adsorption of As on biochar is a function of several factors, including the concentration and type of oxygen functional groups, zeta potential, O/C ratios, (O + N)/C ratios and polarity indices [(O + N)/C] [13, 23, 55, 57, 77].

3.2. Use of modified biochar for As treatment

Many different surface modifications have been examined for As sorption onto biochars. Among those, a zero valent Fe coating is the most prominent, because Fe is one of the most effective materials for As removal from water [12, 56, 78-81]. However, the materials and methods used for Fe coating vary. In one study, a hematite suspension was mixed with a feedstock and pyrolyzed together to induce thermal activation of hematite and maghemite formation [56]. Evaporative methods and direct hydrolysis are common procedures used to produce iron-oxide amended biochars [12, 78-79]. Other than iron, AlOOH, manganese salts, or minerals have been used for surface activation of biochars to remove As [80, 82]. KOH has been used to activate the surface of municipal solid waste biochars by mixing them with 2 M KOH for 1 h [37]. Activation of biochar by producing nano-composites may lead to an increase in the adsorption capacity due to a high surface area of the nano material [81-82].

Activation of biochar as an amendment has enhanced As sorption as shown in Table 3.

Table 3 Arsenic adsorption capacities of modified biochars



Biochar	Type of Biochar	Temp. °C	As(III) /As(V)	pH	BET surface area (m ² /g)	Pore Volume (cm ³ /g)	Initial Concentration (mg/L)	Metal	Optimum Adsorbent dose (g/L)	Maximum Removal mg/g	Reference
Mn Oxide modified biochar	Pine wood	600	As(V)	NA	463	0.022 cc/g	10		2.5	0.59	[56]
Birnessite modified biochar	Pine wood	600	As(V)	NA	67.4	0.066 cc/g	10		2.5	0.91	[56]
Hydrogel biochar	Rice husk	300	As(V)	6.7-7	51	0.058	1-150		0.167-16.7	28	[83]
Magnetic biochar	Pine wood	600	As(V)	NA	193.1	NA	20		2.5	0.43	[80]
NZVI-biochar	Bamboo	400	As(V)	NA	NA	NA	5-400		2	24	[81]
KOH activated biochar	Municipal solid waste		As(III)	8.3	49.1	0.357	50		5	31	[37]
Fe-biochar	Hickory chips	550	As(V)	NA	NA	NA	55		1	2.16	[79]
Empty fruit bunch-Fe biochar	Fruit bunch	700	As(III)	NA	NA	NA	50		5	31.4	[13]
			As(V)	NA	NA	NA	50		5	15.2	
Rice husk-Fe biochar	Rice husk	700	As(III)	NA	NA	NA	50		5	30.7	
			As(V)	NA	NA	NA	50		5	16.9	
AlOOH-biochar	Cotton wood	600	As(V)	NA	NA	NA	50		2	17	[82]
Magnetic biochar	Cotton wood	600	As(V)	NA	NA	NA	50		2	3.1	[82]
Fe coated Rice Husk biochar	Rice husk	550	As(V)		77.3	NA	2		0.5	6.0	[78]

Chemical activation of biochar is so far the sole method that has been used to improve the adsorption capacity via increasing surface area, pore volume, pore size distribution, and partially by changing functional groups on the surface of biochars [18]. The electrostatic interactions are suggested to be the main mechanism that triggers the immobilization of various heavy metal(loid)s on either positively or negatively charged biochar surfaces [77]. Enhanced surface area and pore volume may enable the diffusion of As into the biochar pores, thereby providing more metal (loid)active sites to bind metal ions on the biochar surface [84]. Thus, the adsorption of As on biochar can be optimized by expanding the surface area and pore size distribution (micro-, meso- and macro-). However, poor adsorption of As was shown in some materials that are characterized with high surface area and pore volume, suggesting that pore size distribution is an additional parameter that influences sorption capacity [17, 77]. This implies that many factors can govern the adsorption mechanisms resulting in great variation in the sorption capacities of the adsorbent.. Surface complexation with functional groups of biochar is possibly responsible for the adsorption of As ions [12, 82]. Biochars produced at low temperatures are rich in oxygenated functional groups, such as carboxylic and phenolic groups [17, 21].



The ionizable functional groups of biochar surface may acquire charge through protonation and deprotonation with solutes [85]. Amine groups are one of such surface functional groups which may present on biochar surfaces, can protonate at acidic pHs and result electrostatic attractions with negatively charged arsenate species (reactions 14) [86]. However, further studies are extremely necessary in revealing the actual mechanism in molecular level. Hence, the elucidation of molecular-level interactions controlling the sorption of As on biochar would be of major theoretical and practical interest in future research.



Assuming the presence of different types of acidic surface sites in hydrated biochar as C_iOH surface reactions for As complexation may be written as follows;



Where C is any of the surface active sites that were taken for the adsorption, here it may be carbon functional group. In some cases biochar is supported with titanium dioxide as a photocatalyst [87]. If TiO_2 is impregnated to biochar, the most common hydrated Ti(IV) may react with As(III) and As(V) and the postulated mechanisms are as equations 17-20 [88].






4. Application of biochar in As contaminated soil

Pot experiments with different plants such as ryegrass (*Lolium perenne* L.), tomato (*Solanum lycopersicum* L.), *Miscanthus giganteus*, and maize (*Zea mays* L.) have been conducted with As-contaminated soils using biochars produced at various temperatures. Soils that have been used were contaminated by geogenic As, including mine soil [89-90], as well as industrially contaminated soil [91], and As containing pesticides applied soils [92-93].

4.1. Response of soil physio-chemical properties of As-contaminated soils to biochar

High extractable dissolved organic carbon (DOC), Ca, Mg, K, SO_4^{2-} contents were observed in soils amended with wood and bioenergy derived biochars [92, 94-95]. A rapid reduction of As(V) to As(III) in biochar amended soils has been observed, because organic matter and various functional groups such as phenolic, alcoholic and carboxylic associated with the biochar can act as electron donors to govern the reduction reactions (reactions 21, 22, 23) [96]. Because of such naturally occurring redox reactions in biochar incorporated soils, the mobility of As(III) species is increased, while As(V) is strongly retained, thereby reducing the leachate concentrations of As(V) and increasing the bioavailability of As(III) in such biochar-soil systems [96-97].



Cation exchange capacity (CEC) and pH of soils demonstrate a considerable increase with increasing application rates of biochar which may contribute to controversial interpretations. High pH may lower the positive charge on soil-BC system which could reduce the anionic As sorption whereas high EC may induce more cations to be present and that may induce As sorption or precipitation [98]. However, none of the studies have focused their attention on the influence of the increase in pH and CEC by the addition of BC on As sorption. In some previous studies the addition of biochar as a soil amendment decreased the DOC in pore water collected from field and pot trials, since soil carbon pool is relatively stable and insoluble [94, 99-100]. However, it was shown that Orchard Prune residue biochar increased the organic matter content by approximately >50%, which might increase the mobilization of As(V) and move it into soil solution [94]. The interactions of As with phosphate ions, which are associated with biochar, are

also of concern, because phosphate ions are linked with the mobility and bioavailability of As species [101-102]. In a solution culture, the presence of high contents of P reduced the mobility and bioavailability of As(V) due to their competitive effects that allowed As(V) to be more retained and, and, consequently, it was less available for uptake by plants. However, application of P in soil systems increased the dissolution of As(V), thereby enhancing its bioavailability [101]. Hence, it is clear that the interactions of As-P are dependent on the environmental system as well as the existing concentrations of As and P [102].

Studies on biochar ageing in As contaminated soils are scarce. However, the age of the biochar likely determines its surface charge, which is an essential parameter to describe to understand the adsorption behavior of various ionic forms of contaminants [103]. When biochars are placed in soil, porous organomineral layers form on the surface (Joseph et al 2013). These have a high concentration of function groups that can bind with heavy metals [104]. However, studies have revealed contradictory data, some of which indicate that ageing of biochar does not increase in surface charge [103], whereas other studies have demonstrated an increase in surface charge with ageing biochar [105-106]. Additional experiments on soil ageing with biochar may develop a better mechanistic understanding of the interactions of biochar and soil.

4.2. Role of biochar on As in soil

The application of biochar in many As contaminated systems results in an increase in its mobility and bioavailability [93-94, 107-108]. Hence, this suggests that future researchers should not apply some biochar types in the field for remediation of As contaminated soils [89]. To solve this conflicting behavior of biochar-As systems, recent studies have suggested the use of biochars along with phytoremediation for decontamination of soils with As [94, 96]. Although

similar As concentrations can be found in soils, inherent differences can be observed in soil systems, which are likely due to differences in soil properties such as texture, P, pH, Fe, OM, and DOC before and after biochar additions, and they may influence As mobility and bioavailability [91]. At the same time, As mobility/sink in soil depends strictly on the co-existence of organic/inorganic sulfur and iron [109-111]. Understanding molecular level characteristics may provide information concerning the mechanisms involved, but studies are limited at this level [109].

Biochar ageing studies have confirmed that high CEC in soil leads to the formation of stable biochar-metal complexes. Reduction in As concentration in the shoots of maize (*Zea mays* L.) plants grown in biochar amended sandy soil was observed, which was mainly attributed to the adsorption of As onto the biochar surfaces [107]. The results showed a decrease in As uptake by the maize depending on the application rate. In a soil rich in As due to the long-term application of pesticides, bioavailability of As for phytoextraction by *Lolium perenne* L. was studied [92]. The authors showed that the bioavailability of As with low-temperature (350 °C) derived biochars was less than that from biochars derived from high-temperatures (650 °C) (Reduction in bioavailability were 100% and 70% respectively compared to the control) [92]. The amount of water-extractable As can be reduced temporarily because of the precipitation of As with metal cations, such as Ca^{2+} . However, they may readily re-dissolve, releasing As again to the aqueous solutions [92, 112]. In the ryegrass study [76], when the application rate of biochar was increased from 30 to 60%, the concentrations of As in shoot tissues of ryegrass were increased indicating that higher application rates would be suitable for increasing As phytoextraction in soils.

Application of biochar produced from orchard prune residue as a soil amendment in an As contaminated mine soil increased the concentrations of As in pore water (500 - 2000 $\mu\text{g L}^{-1}$) and

decreased the accumulation of As in roots and shoots of tomato plants (*Solanum lycopersicum* L.) grown in the mining soil. This interesting observation was explained by the formation of soluble As-DOC complexes, which are mobile but may not be able to diffuse through the tissues of tomato plants (Fig. 3). Accumulation of As in tomato fruits was low due to reduction of the phyto-availability of As in the biochar treated mine soil. [89]. Contents of P and Fe in soils can be increased by over 20-fold by the addition of biochar [89, 113]. Macro-, micro- and nanoporous structure of biochar surfaces can facilitate the reduction of Fe [114] and Mn species found in soils [66], which results in a negative Eh value. Negative Eh conditions promote the reduction of As(V) to As(III) species which is not readily adsorbed in soils and hence under negative redox potentials, As species are more mobile in soils [115].

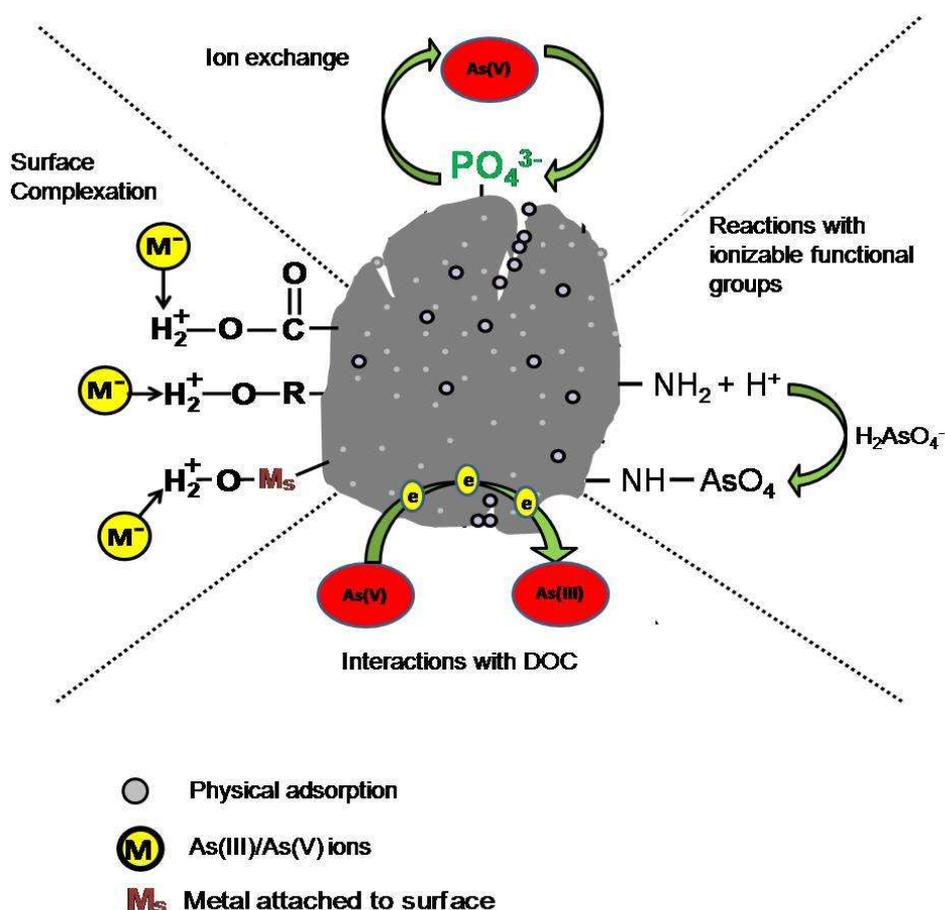


Fig. 3. Graphical illustration of postulated mechanisms for As adsorption on biochar surface

However, some studies have demonstrated insignificant effects of fresh biochar on As adsorption compared to soils without biochar [91, 103]. This suggests a possibility of As complexation with DOC from biochar, which can be prominent in soils with high organic C. Slight changes in soil pH may not influence the sorption of As in biochar amended soils [103]. Competition of DOC, P, and As for the vacant sorption sites on soil surfaces can lead to an increase of the solubility of As in soil [91, 94]. In some cases, biochar application may induce solubilization of As in the pore water (>2500 mg/L), which may be attributed to high pH. However, in a study where a

compost amendment was used, As toxicity was reduced due to a reduction in extractable metals and an increase in soluble P [91, 94]. More detailed molecular level studies are needed to provide insights into the influence of ageing, DOC, P interactions, and microorganisms on the soil-As interactions.

4.3. Response of microbiological properties in biochar amended As contaminated soils

Biochar amendments have been found to have less of an effect on microbial biomass nitrogen (MBN) than microbial biomass carbon (MBC) [116]. A long-term field study showed that the MBC:MBN was increased by biochar, thereby reducing the temporal variability of microbial growth in the environment [116].

Only a few studies have been carried out on the responses of microbes in biochar amended As contaminated soils [92-93, 117-118]. Biochar amendments in soils can increase microbial activity [116]. The improvement of both plant growth and soil microbial activity may be due to nutrient supply by biochar (K^+ , Ca^{2+} , Mg^{2+}) and the labile C fraction of biochar that is considered as a food source of microbes [92]. Microbial activity in soils can also affect the redox conditions of the soil as well as speciation of As. Hence, microbial activity can lead to reduction of As(V) to As(III), thereby impacting the mobility and bioavailability of As. Dehydrogenase (DHA) activity is considered to serve as an indicator of total microbial activity. In one study [76], addition of biochar produced under both low and high pyrolytic temperatures resulted in an increase in DHA compared to the control. However, no significant difference was observed with the application rate [92]. The labile fraction of carbon (C), which is higher in low temperature derived biochar than in high temperature biochar, can act as an energy source for soil microorganisms [119]. Such a readily available energy source can enhance microbial activity

resulting in a higher soil DHA, which may contribute to the short-term reduction in the water-extractable concentration of As [92]. In a study regarding the speciation and reduction of As(V) in As contaminated mine tailing sediments amended with biochar, the populations of As(V) reducing bacteria, *Geobacter*, *Anaeromyxobacter*, *Desulfosporosinus*, and *Pedobacter*, were increased after the addition of biochar and this biochar-bacterial consortium stimulated the reduction of As(V) to As(III) and increased the concentrations of dissolved organic matter in the biochar amended mine sediments [117]. More research is necessary to understand mechanistically the soil-microbial activities that are associated with biochar amended soils with As.

4.4. Summary and future research

Many papers have been published on the applications of biochar to remediate soil and water systems that are polluted by toxic organic and inorganic contaminants. However, few laboratory or field studies have been done regarding the interactions of biochar and metalloids. More research is needed to study biochar-As interactions. The present review focuses on recent developments related to the interactions of biochar and As species found in water and soil systems.

Arsenic adsorption properties are affected by pyrolytic temperature, residence time, feedstock, and pyrolysis technology. Depending on the pyrolytic temperature, biochar can be used as an adsorbent for arsenic. Low-temperature biochars are more effective in As sorption than high-temperature biochars. Adsorption of As is affected by the solution pH, adsorbate and adsorbent dose, and equilibration time. Much attention has been given to enhancing As sorption by modifying the biochar surface. Modifications have been performed using different coatings of

iron, including nano zero valent iron and other materials such as Al and Mn. The most predominant adsorption mechanisms for As by biochar include electrostatic attraction, ion-exchange, physical adsorption, and chemical bonding (complexation and/or precipitation). However, due to the low surface area and weak mechanical properties, biochar has not been considered as promising as activated carbon in the water treatment. Modifications to biochar which increase the surface area and mechanical properties, may allow it to be used in water treatment suitable for oxy-anions and metalloids hence, the research towards such would be in high interest in terms of material science point of view. The studies in the literature for biochar-As interaction in water consist of rather different parameters and methods from study to study and hence, comparison is impossible. Also, no studies have focused the attention on organic arsenic removal using biochar and that would be promising for future research. Enhanced biotransformation of methylated arsenic by bacteria incorporated biochar may be a potential future study since biochar provides residency for microbes. Molecular level interactions of biochar-functional groups need to be studied more, which may provide clear information on the mechanisms involved.

Biochar-induced changes in soil physio-chemical properties may influence the bioavailability and phytotoxicity of As. Contrasting results have been reported in terms of As mobility in soil due to changes in other solutes in the soil solution, DOC, pH, CEC, and Phosphate. Even though the use of biochar as an adsorbent is increasing, a number of research gaps exist. More research is needed to confirm the use of nano-biochar composites in the environment. Low-cost modifications such as using steam-activation, acid-activation, or other activations may facilitate As remediation. Activation by nitrogen may provide amide functional groups which could be

useful in increasing arsenic sorption, however, no research has been focused. Hence, more attention need to be driven towards assessing interaction of different arsenic species on nitrogen activated biochars. Interactions with rhizosphere microbes, iron plaques interactions with biochar in soil needs fundamental molecular level attention may be using advanced techniques like Nanoscale secondary ion mass spectrometry etc. Speciation and fractionation of different arsenic species in soil may influence the mobility, bioavailability, fate and transport with the presence of biochar due to the changes in soil chemistry, which have no attention paid yet. The interaction of biochar and soil microbes in relation to the immobilization of toxic As species, including the use of methylated and thio-arsenates, need to be studied. None of the studies have performed any cost-benefit analysis for biochar and other materials which can be considered as a gap in the research related to As-biochar interaction.

References

- [1] B.K. Mandal, K.T. Suzuki, Arsenic round the world: a review, *Talanta* 58(1) (2002) 201-235.
- [2] M.R. Perry, V.K. Prajapati, J. Menten, A. Raab, J. Feldmann, D. Chakraborti, S. Sundar, A.H. Fairlamb, M. Boelaert, A. Picado, Arsenic Exposure and Outcomes of Antimonial Treatment in Visceral Leishmaniasis Patients in Bihar, India: A Retrospective Cohort Study, *PLoS Negl. Trop. Dis.* 9(3) (2015) e0003518.
- [3] Y. Chen, J.H. Graziano, F. Parvez, M. Liu, V. Slavkovich, T. Kalra, M. Argos, T. Islam, A. Ahmed, M. Rakibuz-Zaman, R. Hasan, G. Sarwar, D. Levy, A. van Geen, H. Ahsan, Arsenic exposure from drinking water and mortality from cardiovascular disease in Bangladesh: prospective cohort study, *BMJ* 342 (2011).
- [4] G. Dyer, A review of: "Chemistry of the Elements. N.N. Greenwood and A. Earnshaw, Pergamon Press, Oxford, 1984. XXI + 1542 pp. £75 Hardcover, £19.50 Flexicover", *Syn. React. Inorg. Met.* 15(9) (1985) 1261-1262.
- [5] B. Planer-Friedrich, A.C. Scheinost, Formation and Structural Characterization of Thioantimony Species and Their Natural Occurrence in Geothermal Waters, *Environmental Science & Technology* 45(16) (2011) 6855-6863.
- [6] Z. Šlejkovec, E. Kápolna, I. Ipolyi, J.T. van Elteren, Arsenosugars and other arsenic compounds in littoral zone algae from the Adriatic Sea, *Chemosphere* 63(7) (2006) 1098-1105.

- [7] I. Herath, M. Vithanage, J. Bundschuh, J.P. Maity, P. Bhattacharya, Natural Arsenic in Global Groundwaters: Distribution and Geochemical Triggers for Mobilization, *Curr. Pollut. Rep.* (2016) 1-22.
- [8] S. Mahimairaja, N.S. Bolan, D.C. Adriano, B. Robinson, Arsenic Contamination and its Risk Management in Complex Environmental Settings, in: L.S. Donald (Ed.), *Advances in Agronomy*, Academic Press 2005, pp. 1-82.
- [9] C. Mikutta, P.N. Mandaliev, N. Mahler, T. Kotsev, R. Kretzschmar, Bioaccessibility of Arsenic in Mining-Impacted Circumneutral River Floodplain Soils, *Environ. Sci. Technol.* 48(22) (2014) 13468-13477.
- [10] E. Agrafioti, D. Kalderis, E. Diamadopoulos, Arsenic and chromium removal from water using biochars derived from rice husk, organic solid wastes and sewage sludge, *Journal of Environmental Management* 133 (2014) 309-314.
- [11] D. Mohan, C.U. Pittman Jr, Arsenic removal from water/wastewater using adsorbents—A critical review, *J. Hazard. Mater.* 142(1–2) (2007) 1-53.
- [12] M. Zhang, B. Gao, S. Varnosfaderani, A. Hebard, Y. Yao, M. Inyang, Preparation and characterization of a novel magnetic biochar for arsenic removal, *Bioresource Technol.* 130(0) (2013) 457-462.
- [13] A.W. Samsuri, F. Sadegh-Zadeh, B.J. Seh-Bardan, Adsorption of As(III) and As(V) by Fe coated biochars and biochars produced from empty fruit bunch and rice husk, *J. Environ. Chem. Eng.* 1(4) (2013) 981-988.
- [14] M. Vithanage, R. Chandrajith, A. Bandara, R. Weerasooriya, Mechanistic modeling of arsenic retention on natural red earth in simulated environmental systems, *J. Colloid Interface Sci.* 294(2) (2006) 265-272.
- [15] J.-H. Huang, Impact of Microorganisms on Arsenic Biogeochemistry: A Review, *Water Air Soil Pollut.* 225(2) (2014) 1-25.
- [16] D. Mohan, K.P. Singh, V.K. Singh, Trivalent chromium removal from wastewater using low cost activated carbon derived from agricultural waste material and activated carbon fabric cloth, *J. Hazard. Mater.* 135(1–3) (2006) 280-295.
- [17] M. Ahmad, A.U. Rajapaksha, J.E. Lim, M. Zhang, N. Bolan, D. Mohan, M. Vithanage, S.S. Lee, Y.S. Ok, Biochar as a sorbent for contaminant management in soil and water: A review, *Chemosphere* 99(0) (2014) 19-33.
- [18] A.U. Rajapaksha, S.S. Chen, D.C.W. Tsang, M. Zhang, M. Vithanage, S. Mandal, B. Gao, N.S. Bolan, Y.S. Ok, Engineered/designer biochar for contaminant removal/immobilization from soil and water: Potential and implication of biochar modification, *Chemosphere* 148 (2016) 276-291.
- [19] J. Lehmann, S. Joseph, Biochar for environmental management: An Introduction, in: J. Lehmann, S. Joseph (Eds.) *Biochar for environmental management: science and technology* Earthscan, London, 2009, pp. 1-9.
- [20] S. Jeffery, F.G.A. Verheijen, M. van der Velde, A.C. Bastos, A quantitative review of the effects of biochar application to soils on crop productivity using meta-analysis, *Agric. Ecosyst. Environ.* 144(1) (2011) 175-187.
- [21] X. Tan, Y. Liu, G. Zeng, X. Wang, X. Hu, Y. Gu, Z. Yang, Application of biochar for the removal of pollutants from aqueous solutions, *Chemosphere* 125(0) (2015) 70-85.

- [22] M. Inyang, E. Dickenson, The potential role of biochar in the removal of organic and microbial contaminants from potable and reuse water: A review, *Chemosphere* 134 (2015) 232-240.
- [23] D. Mohan, A. Sarswat, Y.S. Ok, C.U. Pittman Jr, Organic and inorganic contaminants removal from water with biochar, a renewable, low cost and sustainable adsorbent – A critical review, *Bioresource Technol.* 160 (2014) 191-202.
- [24] E. Marris, Putting the carbon back: Black is the new green, *Nature* 442(7103) (2006) 624-626.
- [25] B. Glaser, J.J. Birk, State of the scientific knowledge on properties and genesis of Anthropogenic Dark Earths in Central Amazonia (terra preta de Índio), *Geochim. Cosmochim. Ac.* 82 (2012) 39-51.
- [26] C. Steiner, W.G. Teixeira, J. Lehmann, T. Nehls, J.L.V. de Macêdo, W.E. Blum, W. Zech, Long term effects of manure, charcoal and mineral fertilization on crop production and fertility on a highly weathered Central Amazonian upland soil, *Plant and Soil* 291(1-2) (2007) 275-290.
- [27] J. Lehmann, J.P. da Silva Jr, C. Steiner, T. Nehls, W. Zech, B. Glaser, Nutrient availability and leaching in an archaeological Anthrosol and a Ferralsol of the Central Amazon basin: fertilizer, manure and charcoal amendments, *Plant and Soil* 249(2) (2003) 343-357.
- [28] P. Khare, D.K. Goyal, Effect of high and low rank char on soil quality and carbon sequestration, *Ecol. Eng.* 52(0) (2013) 161-166.
- [29] I. Stavi, R. Lal, Agroforestry and biochar to offset climate change: a review, *Agron. Sustain. Dev.* 33(1) (2013) 81-96.
- [30] M. Rizwan, S. Ali, M.F. Qayyum, M. Ibrahim, M. Zia-ur-Rehman, T. Abbas, Y.S. Ok, Mechanisms of biochar-mediated alleviation of toxicity of trace elements in plants: a critical review, *Environ. Sci. Pollut. Res.* 23(3) (2016) 2230-2248.
- [31] M. Hussain, M. Farooq, A. Nawaz, A.M. Al-Sadi, Z.M. Solaiman, S.S. Alghamdi, U. Ammara, Y.S. Ok, K.H.M. Siddique, Biochar for crop production: potential benefits and risks, *J. Soils Sediments* (2016) 1-32.
- [32] S. Meyer, B. Glaser, P. Quicker, Technical, Economical, and Climate-Related Aspects of Biochar Production Technologies: A Literature Review, *Environ. Sci. Technol.* 45(22) (2011) 9473-9483.
- [33] A.U. Rajapaksha, M. Vithanage, J.E. Lim, M.B.M. Ahmed, M. Zhang, S.S. Lee, Y.S. Ok, Invasive plant-derived biochar inhibits sulfamethazine uptake by lettuce in soil, *Chemosphere* 111 (2014) 500-504.
- [34] M.H. Duku, S. Gu, E.B. Hagan, Biochar production potential in Ghana—A review, *Renewable and Sustainable Energy Reviews* 15(8) (2011) 3539-3551.
- [35] D.W. Rutherford, R.L. Wershaw, C.E. Rostad, C.N. Kelly, Effect of formation conditions on biochars: Compositional and structural properties of cellulose, lignin, and pine biochars, *Biomass Bioenergy* 46(0) (2012) 693-701.
- [36] M. Ahmad, S.S. Lee, A.U. Rajapaksha, M. Vithanage, M. Zhang, J.S. Cho, S.-E. Lee, Y.S. Ok, Trichloroethylene adsorption by pine needle biochars produced at various pyrolysis temperatures, *Bioresource Technology* 143 (2013) 615-622.
- [37] H. Jin, S. Capareda, Z. Chang, J. Gao, Y. Xu, J. Zhang, Biochar pyrolytically produced from municipal solid wastes for aqueous As(V) removal: Adsorption property and its improvement with KOH activation, *Bioresource Technol.* 169(0) (2014) 622-629.

- [38] D. Laird, P. Fleming, B. Wang, R. Horton, D. Karlen, Biochar impact on nutrient leaching from a Midwestern agricultural soil, *Geoderma* 158(3–4) (2010) 436-442.
- [39] Downie A, Crosky A, M. P, Physical properties of biochar, in: J. Lehmann, S. Joseph (Eds.), *Biochar for Environmental Management: Science and Technology*, Earthscan, London, UK2009, pp. 13-32.
- [40] J.E. Amonette, S. Joseph, Characteristics of biochar: Microchemical properties, in: J. Lehmann, J. S. (Eds.), *Biochar for Environmental Management: Science and Technology*, Earthscan, London, UK2009, pp. 33-52.
- [41] M. Uchimiya, A. Orlov, G. Ramakrishnan, K. Sistani, In situ and ex situ spectroscopic monitoring of biochar's surface functional groups, *J. Anal. Appl. Pyrolysis* 102(0) (2013) 53-59.
- [42] W.-K. Kim, T. Shim, Y.-S. Kim, S. Hyun, C. Ryu, Y.-K. Park, J. Jung, Characterization of cadmium removal from aqueous solution by biochar produced from a giant *Miscanthus* at different pyrolytic temperatures, *Bioresource Technol.* 138(0) (2013) 266-270.
- [43] B. Glaser, J. Lehmann, W. Zech, Ameliorating physical and chemical properties of highly weathered soils in the tropics with charcoal – a review, *Biol. Fert. Soils* 35(4) (2002) 219-230.
- [44] M. Ahmad, S.S. Lee, X. Dou, D. Mohan, J.-K. Sung, J.E. Yang, Y.S. Ok, Effects of pyrolysis temperature on soybean stover- and peanut shell-derived biochar properties and TCE adsorption in water, *Bioresource Technol.* 118(0) (2012) 536-544.
- [45] S. Malghani, G. Gleixner, S.E. Trumbore, Chars produced by slow pyrolysis and hydrothermal carbonization vary in carbon sequestration potential and greenhouse gases emissions, *Soil Biol. Biochem.* 62(0) (2013) 137-146.
- [46] M.D. Huff, S. Kumar, J.W. Lee, Comparative analysis of pinewood, peanut shell, and bamboo biomass derived biochars produced via hydrothermal conversion and pyrolysis, *J. Environ. Manage.* 146(0) (2014) 303-308.
- [47] Z. Liu, F.-S. Zhang, J. Wu, Characterization and application of chars produced from pinewood pyrolysis and hydrothermal treatment, *Fuel* 89(2) (2010) 510-514.
- [48] I. Bargmann, M.C. Rillig, A. Kruse, J.-M. Greef, M. Kücke, Initial and subsequent effects of hydrochar amendment on germination and nitrogen uptake of spring barley, *Journal of Plant Nutrition and Soil Science* 177(1) (2014) 68-74.
- [49] M.J. Prins, K.J. Ptasinski, F.J.J.G. Janssen, Torrefaction of wood: Part 1. Weight loss kinetics, *Journal of Analytical and Applied Pyrolysis* 77(1) (2006) 28-34.
- [50] A. Uslu, A.P.C. Faaij, P.C.A. Bergman, Pre-treatment technologies, and their effect on international bioenergy supply chain logistics. Techno-economic evaluation of torrefaction, fast pyrolysis and pelletisation, *Energy* 33(8) (2008) 1206-1223.
- [51] S.E. Elaigwu, V. Rocher, G. Kyriakou, G.M. Greenway, Removal of Pb²⁺ and Cd²⁺ from aqueous solution using chars from pyrolysis and microwave-assisted hydrothermal carbonization of *Prosopis africana* shell, *J. Ind. Eng. Chem.* 20(5) (2014) 3467-3473.
- [52] E. Agrafioti, D. Kalderis, E. Diamadopoulos, Arsenic and chromium removal from water using biochars derived from rice husk, organic solid wastes and sewage sludge, *J. of Environ. Manage.* 133(0) (2014) 309-314.
- [53] D. Mohan, C.U. Pittman Jr, M. Bricka, F. Smith, B. Yancey, J. Mohammad, P.H. Steele, M.F. Alexandre-Franco, V. Gómez-Serrano, H. Gong, Sorption of arsenic, cadmium, and lead by chars produced from fast pyrolysis of wood and bark during bio-oil production, *J. Colloid Interface Sci.* 310(1) (2007) 57-73.

- [54] D. Tavares, C. Lopes, J. Coelho, M. Sánchez, A. Garcia, A. Duarte, M. Otero, E. Pereira, Removal of Arsenic from Aqueous Solutions by Sorption onto Sewage Sludge-Based Sorbent, *Water Air Soil Pollut.* 223(5) (2012) 2311-2321.
- [55] N. Van Vinh, M. Zafar, S.K. Behera, H.S. Park, Arsenic(III) removal from aqueous solution by raw and zinc-loaded pine cone biochar: equilibrium, kinetics, and thermodynamics studies, *Int. J. Environ. Sci. Technol.* 12(4) (2015) 1283-1294.
- [56] S. Wang, B. Gao, A.R. Zimmerman, Y. Li, L. Ma, W.G. Harris, K.W. Migliaccio, Removal of arsenic by magnetic biochar prepared from pinewood and natural hematite, *Bioresource Technol.* 175(0) (2015) 391-395.
- [57] N.A. Sari, C.F. Ishak, R.A. Bakar, Characterization of oil palm empty fruit bunch and rice husk biochars and their potential to adsorb arsenic and cadmium, *Am. J. Agric. Biol. Sci.* 9 (2014) 450-456.
- [58] N.A. Sari, C.F. Ishak, R.A. Bakar, Characterization of oil palm empty fruit bunch and rice husk biochars and their potential to adsorb arsenic and cadmium, *Am. J. Agric. Biol. Sci.* 9(3) (2014) 450-456.
- [59] N. Van Vinh, M. Zafar, S.K. Behera, H.-S. Park, Arsenic(III) removal from aqueous solution by raw and zinc-loaded pine cone biochar: equilibrium, kinetics, and thermodynamics studies, *International Journal of Environmental Science and Technology* 12(4) (2015) 1283-1294.
- [60] S. Deng, G. Yu, S. Xie, Q. Yu, J. Huang, Y. Kuwaki, M. Iseki, Enhanced Adsorption of Arsenate on the Aminated Fibers: Sorption Behavior and Uptake Mechanism, *Langmuir* 24(19) (2008) 10961-10967.
- [61] Z. Wei, K. Liang, Y. Wu, Y. Zou, J. Zuo, D.C. Arriagada, Z. Pan, G. Hu, The effect of pH on the adsorption of arsenic(III) and arsenic(V) at the TiO₂ anatase [1 0 1] surface, *Journal of Colloid and Interface Science* 462 (2016) 252-259.
- [62] I. Herath, P. Kumarathilaka, M.I. Al-Wabel, A. Abduljabbar, M. Ahmad, A.R.A. Usman, M. Vithanage, Mechanistic modeling of glyphosate interaction with rice husk derived engineered biochar, *Microporous and Mesoporous Materials* 225 (2016) 280-288.
- [63] J. Luster, K. Kalbitz, B. Lennartz, J. Rinklebe, Properties, processes and ecological functions of floodplain, peatland, and paddy soils, *Geoderma* 228–229 (2014) 1-4.
- [64] S.M. Shaheen, J. Rinklebe, H. Rupp, R. Meissner, Lysimeter trials to assess the impact of different flood–dry–cycles on the dynamics of pore water concentrations of As, Cr, Mo and V in a contaminated floodplain soil, *Geoderma* 228–229 (2014) 5-13.
- [65] J. Rinklebe, S.M. Shaheen, T. Frohne, Amendment of biochar reduces the release of toxic elements under dynamic redox conditions in a contaminated floodplain soil, *Chemosphere* In press (2015).
- [66] S.D. Joseph, M. Camps-Arbestain, Y. Lin, P. Munroe, C.H. Chia, J. Hook, L. van Zwieten, S. Kimber, A. Cowie, B.P. Singh, J. Lehmann, N. Foidl, R.J. Smernik, J.E. Amonette, An investigation into the reactions of biochar in soil, *Soil Res.* 48(7) (2010) 501-515.
- [67] S. Joseph, O. Husson, E.R. Graber, L. Van Zwieten, S. Taherymoosavi, T. Thomas, S. Nielsen, J. Ye, G. Pan, C. Chia, The electrochemical properties of biochars and how they affect soil redox properties and processes, *Agronomy* 5(3) (2015) 322-340.
- [68] L. Klüpfel, M. Keiluweit, M. Kleber, M. Sander, Redox Properties of Plant Biomass-Derived Black Carbon (Biochar), *Environmental Science & Technology* 48(10) (2014) 5601-5611.

- [69] S. Joseph, E.R. Graber, C. Chia, P. Munroe, S. Donne, T. Thomas, S. Nielsen, C. Marjo, H. Rutledge, G.X. Pan, L. Li, P. Taylor, A. Rawal, J. Hook, Shifting paradigms: development of high-efficiency biochar fertilizers based on nano-structures and soluble components, *Carbon Management* 4(3) (2013) 323-343.
- [70] F.A. Petter, B.E. Madari, Biochar: Agronomic and environmental potential in Brazilian savannah soils, *Revista Brasileira de Engenharia Agrícola e Ambiental* 16(7) (2012) 761-768.
- [71] Y. Li, S. Yu, J. Strong, H. Wang, Are the biogeochemical cycles of carbon, nitrogen, sulfur, and phosphorus driven by the “FeIII–FeII redox wheel” in dynamic redox environments?, *Journal of Soils and Sediments* 12(5) (2012) 683-693.
- [72] L. Van Zwieten, S. Kimber, S. Morris, K.Y. Chan, A. Downie, J. Rust, S. Joseph, A. Cowie, Effects of biochar from slow pyrolysis of papermill waste on agronomic performance and soil fertility, *Plant and Soil* 327(1) (2010) 235-246.
- [73] M. Habuda-Stanić, B. Kalajdžić, M. Kuleš, N. Velić, Arsenite and arsenate sorption by hydrous ferric oxide/polymeric material, *Desalination* 229(1) (2008) 1-9.
- [74] J.A. Wilkie, J.G. Hering, A collection of papers presented at the Symposium on Colloidal and Interfacial Phenomena in Aquatic Environments Adsorption of arsenic onto hydrous ferric oxide: effects of adsorbate/adsorbent ratios and co-occurring solutes, *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 107 (1996) 97-110.
- [75] A. Manceau, The mechanism of anion adsorption on iron oxides: Evidence for the bonding of arsenate tetrahedra on free Fe(O, OH)₆ edges, *Geochimica et Cosmochimica Acta* 59(17) (1995) 3647-3653.
- [76] S. Dixit, J.G. Hering, Comparison of Arsenic(V) and Arsenic(III) Sorption onto Iron Oxide Minerals: Implications for Arsenic Mobility, *Environmental Science & Technology* 37(18) (2003) 4182-4189.
- [77] E. Agrafioti, D. Kalderis, E. Diamadopoulou, Ca and Fe modified biochars as adsorbents of arsenic and chromium in aqueous solutions, *J. Environ. Manage.* 146(0) (2014) 444-450.
- [78] C.O. Cope, D.S. Webster, D.A. Sabatini, Arsenate adsorption onto iron oxide amended rice husk char, *Sci. Total Environ.* 488–489(0) (2014) 554-561.
- [79] X. Hu, Z. Ding, A.R. Zimmerman, S. Wang, B. Gao, Batch and column sorption of arsenic onto iron-impregnated biochar synthesized through hydrolysis, *Water Res.* 68(0) (2015) 206-216.
- [80] S. Wang, B. Gao, Y. Li, A. Mosa, A.R. Zimmerman, L.Q. Ma, W.G. Harris, K.W. Migliaccio, Manganese oxide-modified biochars: Preparation, characterization, and sorption of arsenate and lead, *Bioresource Technol.* 181(0) (2015) 13-17.
- [81] Y. Zhou, B. Gao, A.R. Zimmerman, X. Cao, Biochar-supported zerovalent iron reclaims silver from aqueous solution to form antimicrobial nanocomposite, *Chemosphere* 117(0) (2014) 801-805.
- [82] M. Zhang, B. Gao, Removal of arsenic, methylene blue, and phosphate by biochar/AlOOH nanocomposite, *Chem. Eng. J.* 226(0) (2013) 286-292.
- [83] M.L. Sanyang, W.A.W.A.K. Ghani, A. Idris, M.B. Ahmad, Hydrogel biochar composite for arsenic removal from wastewater, *Desalination Water Treat.* (2014) 1-15.
- [84] L. Trakal, D. Bingöl, M. Pohořelý, M. Hruška, M. Komárek, Geochemical and spectroscopic investigations of Cd and Pb sorption mechanisms on contrasting biochars: Engineering implications, *Bioresource Technol.* 171(0) (2014) 442-451.

- [85] M. Vithanage, A.U. Rajapaksha, M. Ahmad, M. Uchimiya, X. Dou, D.S. Alessi, Y.S. Ok, Mechanisms of antimony adsorption onto soybean stover-derived biochar in aqueous solutions, *Journal of Environmental Management* 151 (2015) 443-449.
- [86] A. Tyłak, P. Oleszczuk, R. Dobrowolski, Sorption and desorption of Cr(VI) ions from water by biochars in different environmental conditions, *Environmental Science and Pollution Research International* 22(8) (2015) 5985-5994.
- [87] J.R. Kim, E. Kan, Heterogeneous photocatalytic degradation of sulfamethoxazole in water using a biochar-supported TiO₂ photocatalyst, *Journal of Environmental Management* 180 (2016) 94-101.
- [88] P.K. Dutta, A.K. Ray, V.K. Sharma, F.J. Millero, Adsorption of arsenate and arsenite on titanium dioxide suspensions, *Journal of Colloid and Interface Science* 278(2) (2004) 270-275.
- [89] L. Beesley, M. Marmiroli, L. Pagano, V. Pignoni, G. Fellet, T. Fresno, T. Vameralli, M. Bandiera, N. Marmiroli, Biochar addition to an arsenic contaminated soil increases arsenic concentrations in the pore water but reduces uptake to tomato plants (*Solanum lycopersicum* L.), *Sci. Total Environ.* 454-455(0) (2013) 598-603.
- [90] R. Zheng, Z. Chen, C. Cai, X. Wang, Y. Huang, B. Xiao, G. Sun, Effect of biochars from Rice Husk, Bran and Straw on heavy metal uptake by pot-grown wheat seedling in a historically contaminated soil, *Bioresources* 8(4) (2013) 5965-5982.
- [91] W. Hartley, N.M. Dickinson, P. Riby, N.W. Lepp, Arsenic mobility in brownfield soils amended with green waste compost or biochar and planted with *Miscanthus*, *Environ. Pollut.* 157(10) (2009) 2654-2662.
- [92] S.J. Gregory, C.W.N. Anderson, M. Camps Arbestain, M.T. McManus, Response of plant and soil microbes to biochar amendment of an arsenic-contaminated soil, *Agr. Ecosyst. Environ.* 191(0) (2014) 133-141.
- [93] S.J. Gregory, C.W.N. Anderson, M. Camps-Arbestain, P.J. Biggs, A.R.D. Ganley, J.M. O'Sullivan, M.T. McManus, Biochar in Co-Contaminated Soil Manipulates Arsenic Solubility and Microbiological Community Structure, and Promotes Organochlorine Degradation, *PLoS ONE* 10(4) (2015) e0125393.
- [94] L. Beesley, O.S. Inneh, G.J. Norton, E. Moreno-Jimenez, T. Pardo, R. Clemente, J.J.C. Dawson, Assessing the influence of compost and biochar amendments on the mobility and toxicity of metals and arsenic in a naturally contaminated mine soil, *Environmental Pollution* 186 (2014) 195-202.
- [95] I. Herath, P. Kumarathilaka, A. Navaratne, N. Rajakaruna, M. Vithanage, Immobilization and phytotoxicity reduction of heavy metals in serpentine soil using biochar, *Journal of Soils and Sediments* 15(1) (2015) 126-138.
- [96] G. Choppala, N. Bolan, A. Kunhikrishnan, R. Bush, Differential effect of biochar upon reduction-induced mobility and bioavailability of arsenate and chromate, *Chemosphere* 144 (2016) 374-381.
- [97] N. Bolan, S. Mahimairaja, A. Kunhikrishnan, B. Seshadri, R. Thangarajan, Bioavailability and ecotoxicity of arsenic species in solution culture and soil system: implications to remediation, *Environmental Science and Pollution Research* 22(12) (2015) 8866-8875.
- [98] B. Liang, J. Lehmann, D. Solomon, J. Kinyangi, J. Grossman, B. O'Neill, J.O. Skjemstad, J. Thies, F.J. Luizão, J. Petersen, E.G. Neves, Black Carbon Increases Cation Exchange Capacity in Soils, *Soil Sci. Soc. Am. J.* 70(5) (2006) 1719-1730.

- [99] D.L. Jones, J. Rousk, G. Edwards-Jones, T.H. DeLuca, D.V. Murphy, Biochar-mediated changes in soil quality and plant growth in a three year field trial, *Soil Biol. Biochem.* 45(0) (2012) 113-124.
- [100] N. Karami, R. Clemente, E. Moreno-Jiménez, N.W. Lepp, L. Beesley, Efficiency of green waste compost and biochar soil amendments for reducing lead and copper mobility and uptake to ryegrass, *J. Hazard. Mater.* 191(1–3) (2011) 41-48.
- [101] N. Bolan, S. Mahimairaja, A. Kunhikrishnan, G. Choppala, Phosphorus–arsenic interactions in variable-charge soils in relation to arsenic mobility and bioavailability, *Science of The Total Environment* 463–464 (2013) 1154-1162.
- [102] A.A. Meharg, J. Hartley-Whitaker, Arsenic uptake and metabolism in arsenic resistant and nonresistant plant species, *New Phytologist* 154(1) (2002) 29-43.
- [103] C.L. Nagodavithane, B. Singh, Y. Fang, Effect of ageing on surface charge characteristics and adsorption behaviour of cadmium and arsenate in two contrasting soils amended with biochar, *Soil Res.* 52(2) (2014) 155-163.
- [104] R. Bian, S. Joseph, L. Cui, G. Pan, L. Li, X. Liu, A. Zhang, H. Rutledge, S. Wong, C. Chia, C. Marjo, B. Gong, P. Munroe, S. Donne, A three-year experiment confirms continuous immobilization of cadmium and lead in contaminated paddy field with biochar amendment, *Journal of Hazardous Materials* 272 (2014) 121-128.
- [105] C.-H. Cheng, J. Lehmann, Ageing of black carbon along a temperature gradient, *Chemosphere* 75(8) (2009) 1021-1027.
- [106] C.-H. Cheng, J. Lehmann, M.H. Engelhard, Natural oxidation of black carbon in soils: Changes in molecular form and surface charge along a climosequence, *Geochim. Cosmochim. Ac.* 72(6) (2008) 1598-1610.
- [107] T. Namgay, B. Singh, B.P. Singh, Influence of biochar application to soil on the availability of As, Cd, Cu, Pb, and Zn to maize (*Zea mays* L.), *Soil Res.* 48(7) (2010) 638-647.
- [108] R. Zheng, Z. Chen, C. Cai, B. Tie, X. Liu, B. Reid, Q. Huang, M. Lei, G. Sun, E. Baltrėnaitė, Mitigating heavy metal accumulation into rice (*Oryza sativa* L.) using biochar amendment — a field experiment in Hunan, China, *Environ. Sci. Pollut. Res.* 22(14) (2015) 11097-11108.
- [109] M. Al-Sid-Cheikh, M. Pédrot, A. Dia, H. Guenet, D. Vantelon, M. Davranche, G. Gruau, T. Delhaye, Interactions between natural organic matter, sulfur, arsenic and iron oxides in re-oxidation compounds within riparian wetlands: NanoSIMS and X-ray adsorption spectroscopy evidences, *Sci. Total Environ.* 515–516 (2015) 118-128.
- [110] C. Catrouillet, M. Davranche, A. Dia, M. Bouhnik-Le Coz, E. Demangeat, G. Gruau, Does As(III) interact with Fe(II), Fe(III) and organic matter through ternary complexes?, *J. Colloid Interf. Sci.* 470 (2016) 153-161.
- [111] R.M. Couture, J. Rose, N. Kumar, K. Mitchell, D. Wallschläger, P. Van Cappellen, Sorption of Arsenite, Arsenate, and Thioarsenates to Iron Oxides and Iron Sulfides: A Kinetic and Spectroscopic Investigation, *Environ. Sci. Technol.* 47(11) (2013) 5652-5659.
- [112] L. Beesley, M. Marmiroli, The immobilisation and retention of soluble arsenic, cadmium and zinc by biochar, *Environ. Pollut.* 159(2) (2011) 474-480.
- [113] G. Xu, L.L. Wei, J.N. Sun, H.B. Shao, S.X. Chang, What is more important for enhancing nutrient bioavailability with biochar application into a sandy soil: Direct or indirect mechanism?, *Ecol. Eng.* 52 (2013) 119-124.

- [114] Y. Lin, P. Munroe, S. Joseph, S. Kimber, L. Van Zwieten, Nanoscale organo-mineral reactions of biochars in ferrosol: an investigation using microscopy, *Plant Soil* 357(1-2) (2012) 369-380.
- [115] E. Moreno-Jiménez, E. Esteban, J. Peñalosa, The Fate of Arsenic in Soil-Plant Systems, in: D.M. Whitacre (Ed.), *Reviews of Environmental Contamination and Toxicology*, Springer New York 2012, pp. 1-37.
- [116] Q.-Z. Zhang, F.A. Dijkstra, X.-R. Liu, Y.-D. Wang, J. Huang, N. Lu, Effects of Biochar on Soil Microbial Biomass after Four Years of Consecutive Application in the North China Plain, *PLoS ONE* (2014).
- [117] Z. Chen, Y. Wang, D. Xia, X. Jiang, D. Fu, L. Shen, H. Wang, Q.B. Li, Enhanced bioreduction of iron and arsenic in sediment by biochar amendment influencing microbial community composition and dissolved organic matter content and composition, *Journal of Hazardous Materials* 311 (2016) 20-29.
- [118] J. Lehmann, Y. Kuzyakov, G. Pan, Y.S. Ok, Biochars and the plant-soil interface, *Plant Soil* 395(1) (2015) 1-5.
- [119] J. Lehmann, M.C. Rillig, J. Thies, C.A. Masiello, W.C. Hockaday, D. Crowley, Biochar effects on soil biota – A review, *Soil Biol. Biochem.* 43(9) (2011) 1812-1836.